

Article

# Next-Gen Cellulose Nanofibers from Cellulose Diacetate

Abdushkur Sarymsakov\*, Nurbek Ashurov, Akobirkhon Shukurov, Zilola Nazarova.

Institute of Polymer Chemistry and Physics, Academy of Sciences of the Republic of Uzbekistan, Tashkent, Uzbekistan.

\* Correspondence: [shukuroov@gmail.com](mailto:shukuroov@gmail.com)

**Abstract:** This study explores the formation of cellulose nanofibers from cellulose diacetate (CDA) using electrospinning with acetone-water solvents in ratios of 95:5, 92.5:7.5, and 90:10. By employing saponification in an aqueous potassium hydroxide solution, cellulose II nanofibers were successfully obtained from CDA nanofibers. Comparative analyses using IR spectroscopy and X-ray diffraction revealed distinct properties of CDA and cellulose II nanofibers. The electrospinning process required a solvent with volatility similar to water, leading to the selection of acetone-water mixtures. Electrospinning was conducted under specific conditions: voltage 22–25 kV, flow rate 10–15  $\mu\text{l}/\text{min}$ , temperature 25–40°C, and a 10–15 cm electrode distance. Morphological characteristics were examined via SEM, while IR-Fourier spectroscopy and X-ray diffraction provided structural insights. Results indicated that acetone solutions with 5–10% water were optimal for producing CDA nanofibers. The study highlights the potential practical applications of cellulose II nanofibrous nonwovens in various fields, filling a knowledge gap in the efficient production of cellulose nanofibers from CDA.

**Keywords:** Electrospinning, Nanofibers, Cellulose Diacetate, Cellulose II, IR Spectroscopy.

## 1. Introduction

In recent years, the electrospinning technique has been widely used in the production of nanofibers based on synthetic and natural polymers and their derivatives. Currently, based on nanofibers, the possibility of producing filter materials, composite materials, scaffolds for tissue engineering, biodegradable bactericidal coatings for surgery and medical products, protective clothing, and much more has been shown.

Among natural polymers, it is of great scientific and practical interest to study the possibility of obtaining nanofibers from ethers. Currently, there are known methods for producing nanofibers from di- and triacetyl cellulose and a number of other simple, complex, and mixed cellulose ethers.

Currently of particular interest is the study of the possibility of obtaining nanofibers based on cellulose. This is due to the fact that, due to the high hydrophilicity and large surface area of cellulose nanofibers, there is the possibility of their chemical modification as well as the possibility of their biodegradation.

This report presents the results of studies on the production of cellulose nanofibers based on cellulose diacetate (CDA).

It is known that CDA is highly soluble and forms stable, dilute, and concentrated solutions in a number of organic solvents and their mixtures [1, 2].

**Citation:** Abdushkur Sarymsakov, Nurbek Ashurov, Akobirkhon Shukurov, Zilola Nazarova. Next-Gen Cellulose Nanofibers from Cellulose Diacetate. Central Asian Journal of Medical and Natural Science 2024, 5(3), 372-377.

Received: 6<sup>th</sup> March 2024

Revised: 10<sup>th</sup> April 2024

Accepted: 17<sup>th</sup> May 2024

Published: 24<sup>th</sup> May 2024



**Copyright:** © 2024 by the authors. Submitted for open access publication under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>)

## 2. Materials and Methods

For the electrospinning of nanofibers from CDA solutions, it is necessary to select an appropriate solvent that meets the requirements for the electrospinning of nanofibers from polymer solutions with at least the same volatility as water.

Cellulose diacetate with a degree of substitution or acetylation of 2,6 and a degree of polymerization of 400 from "Fergana Chemical Plant" LLC was selected as a research object. The main reagents used were purchased from Sigma-Aldrich: acetone (99,5%, cat. No. 179124); potassium hydroxide (KOH) ( $\geq 85\%$ , cat. No. 1310-58-3); and to obtain distilled water, a DZ-10L11 distiller from "Huanghua Faithful Instrument Co" Ltd. was used.

Electroforming of CDA solutions of various concentrations containing different amounts of water was carried out on a NanoNC eS-robots device (NanoNC Co. Ltd., Korea) under the following conditions: voltage 22–25 kV, solution flow rate 10–15  $\mu\text{l}/\text{min}$ , chamber temperature 25–40  $^{\circ}\text{C}$ , and distance between anode and cathode 10–15 cm.

The morphological characteristics of the surface of DAC nanofibers were studied using a scanning electron microscope (SEM) (SEM-EVO MA 10) (Germany). Experiments on a scanning electron microscope were carried out as follows: To carry out the sample preparation process, a round holder made of a metal alloy is glued, on top of which a carbon film with a double-sided adhesive surface is glued, onto which the sample is glued. During the measurement, an accelerating voltage (EHT, Extra High Tension) of 10.00 kV was applied, and the working distance (WD, working distance) was 8,5 mm. Images were acquired at various scales using Smart SEM software.

IR-Fourier spectroscopic studies of CDA nanofibers were carried out using an Inventio-S (Bruker) IR-Fourier spectrometer in the spectral range of  $4000 \pm 500 \text{ cm}^{-1}$ . X-ray diffraction analysis of CDA nanofibers was carried out on a Miniflex 600 device (Rigaku) at 40 kV and a current of 15 mA, range  $2\theta = 5\text{--}44^{\circ}$ .

Based on the results of the studied solutions of CDA in their mixtures, acetone containing from 5% to 10% non-solvent water was chosen as a solvent.

## 3. Results

It has been established that a high voltage is applied to a drop of a solution of CDA in acetone containing various amounts of non-solvent water, and the charge on the surface of the solution exceeds the surface tension of the solution drop; a thin stream is drawn out of the solution, which collects on a grounded electrode in the form of a plate after the solvent evaporates. It has been established that the diameter and morphology of the resulting CDA nanofiber are influenced by all variables of the electrospinning process, including the nature of the solvent and its composition, solution concentration, applied voltage, distance between the collector and its bip, as well as the rate of solvent evaporation [3].


It is known that in CDA solutions, macromolecules are never completely and perfectly molecularly dispersed but exist in the form of complex molecular associates, depending on the strength and quantity of intra- and intermolecular interactions [4–6].

Taking into account the above, we studied the rheological properties of CDA solutions of different concentrations in acetone containing different amounts of "non-solvent" water. It is known that the structural viscosity of CDA depends on the degree of structuring and increases sharply with an increase in its molecular weight; the polarity of CDA depends on diacylation and the concentration of the solution in a given solvent, as well as the content of "non-solvent" water in the solvent-acetone. The value of structural viscosity ( $\eta_{\text{str}}$ ) also strongly depends on the nature of the solvent [7].

It has been established that with an increase in the concentration of CDA, the viscosity of the system increases significantly, and the dependence of the viscosity of solutions on

the flow velocity gradient practically does not change and remains constant. The viscosity of CDA solutions, depending on the gradient of the viscous flow rate, changes with the water content in the solvent composition (acetone) and increases in the sequence 5:7,5:10%, regardless of the concentration of the CDA solution. Thus, for the electrospinning of CDA solutions of various concentrations dissolved in acetone containing "non-solvent" water in the range of 5–10%. Based on the results of a study of their rheological properties, a 10% solution prepared in acetone containing 10% water was selected [8].

In Fig. 1, SEM micrographs of nanofibers obtained by electrospinning 10% CDA solutions dissolved in acetone-water mixtures of various volume ratios are presented.

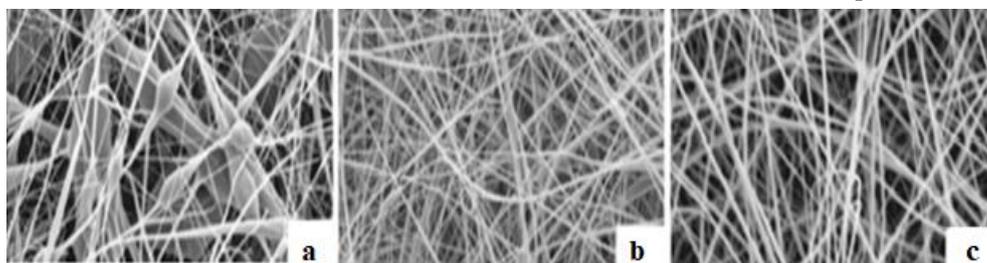

**Figure 1. SEM micrographs of nanofibrous nonwoven fabrics obtained from 10% CDA solutions containing 5% (a), 7,5% (b) and 10% (c) water in acetone.**

As can be seen from fig. 1(a), CDA nanofibers have a heterogeneous composition in diameter containing elongated beads at a water content of 5% in acetone, which is apparently explained by the resistance of the solution jet to the stretching flow during the electrospinning process. When the water content in acetone increases to 7,5% in a 10% CDA solution, more uniform nanofibers with a diameter of 90–430 nm are observed in SEM images of nanofibers. At the same time, almost 50% of the fibers had a diameter of 250 nm [9].

By increasing the water content to 10% in a 10% CDA solution, defect-free homogeneous nanofibers with a diameter of 90–550 nm were obtained by electrospinning.

This, optimal conditions have been established for the formation of nanofibers from 10% solutions of CDA dissolved in acetone containing 10% water with a smooth, relatively hydrophobic surface with an average diameter of 90–550 nm.

Next, we investigated the possibility of obtaining cellulose nanofibers based on CDA nanofibers. It is known that to obtain cellulose nanofibers, it is necessary to select direct solvents that meet the requirements of electrospinning. Known direct solvents for cellulose often have a complex structure; their evaporation temperature is quite high, and solutions of cellulose in known complex solvents do not meet the basic requirements of electrospinning. Taking into account the above, we investigated the possibilities of obtaining cellulose nanofibers based on CDA nanofibers [10].

CDA was obtained by the partial alkaline hydrolysis of triacetylcellulose in an alkaline medium. Under heterogeneous conditions, CDA with a degree of acetylation of 2,4–2,6 were obtained.

We have investigated the possibility of producing hydrated cellulose nanofibers by alkaline hydrolysis of non-woven CDA nanofibers in an alkaline medium. To obtain hydrated cellulose nanofibers, non-woven webs of CDA nanofibers were kept in water at a temperature of 25°C for 12 hours. Next, the canvases were subjected to diacetylation in a 0,1 M aqueous solution of potassium hydroxide at a temperature of 35°C for 1 hour. The diacetylation reaction of CDA nanofibers proceeds at a fairly high speed due to their large surface area, and at the end of the reaction, CDA nanofibers with an acetylation degree of 2,6 are formed into cellulose nanofibers containing 4-6 residual acetyl groups per 100 anhydroglucose units of the cellulose macromolecule. The resulting cellulose

nanofibers with an average diameter of 600–650 nm swollen in a pure environment of 270–20% [11].

IR spectroscopic studies of nanofibers and their hydrolysis in an alkaline medium contribute to the study of the mechanisms and kinetics of the saponification reaction of acetyl groups and changes in the content of CDA ester bonds. Comparative studies of the IR spectra of CDA and cellulose obtained by hydrolysis of CDA nanofibers in an aqueous solution of potassium hydroxide were carried out on an Inventio-S (Bruker) IR Fourier spectrometer in the spectral range of  $4000 \pm 400$   $\text{cm}^{-1}$ , which are presented in fig. 2 [12].


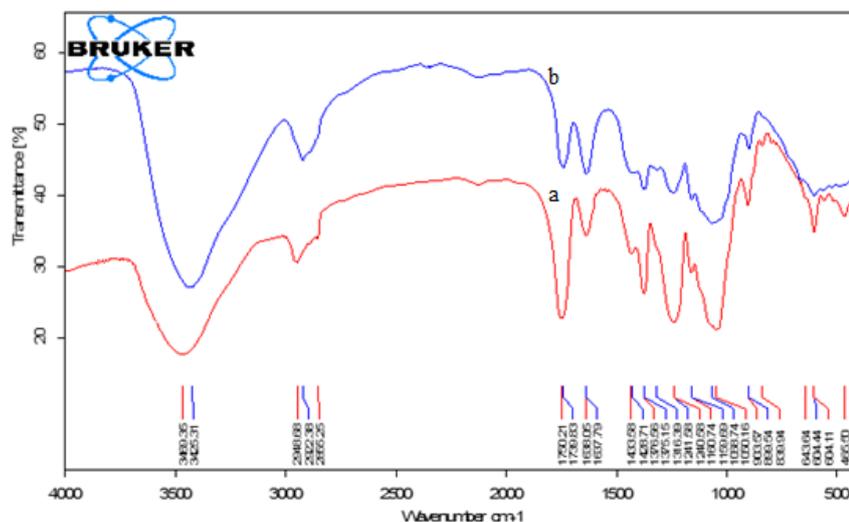


Figure 2. IR spectra of CDA nanofibers (a) and cellulose II nanofibers (b)

As can be seen from fig. 2 in the spectra of CDA nanofibers (a), there are intense bands at 3469, 2948, and 2855  $\text{cm}^{-1}$  characterizing stretching vibrations of acetyl groups, bands at 1050 and 1240  $\text{cm}^{-1}$  characterizing the ester bond, and bands at 1433 and 1376  $\text{cm}^{-1}$  - deformation vibrations of acetyl groups are also visible groups. Intense bands at 1638–1750  $\text{cm}^{-1}$  are attributed to  $\text{-C=O}$  bonds of acetyl groups of CDA, and bands at 465.604 and 643  $\text{cm}^{-1}$  are attributed to out-of-plane bending vibrations of  $\text{-C-OH}$  groups of CDA [13].

In the IR spectra of hydrated cellulose nanofibers obtained by alkaline hydrolysis of CDA nanofibers, fig. 2(b), less intense, in relation to the spectra of CDA, broad blurred bands at 2922, 1739, 1638, and 1428  $\text{cm}^{-1}$  are observed, which are attributed to internal deformation vibrations of  $\text{-CH}_2\text{-}$  in groups  $\text{CH}_2\text{-OH}$ , at 1316 and 1375  $\text{cm}^{-1}$  bending vibrations of  $\text{-C-OH}$  and  $\text{-CH=}$  groups, at 1241, 1159, and 1068  $\text{cm}^{-1}$  stretching vibrations  $\text{=C-O-}$  and 604 and 899  $\text{cm}^{-1}$  attributed to stretching vibrations of methylene groups and deformation vibrations of  $\text{=CH-}$  bonds of pyranose rings of elementary units of cellulose II. Based on the results of the analysis of the IR spectra of CDA nanofibers and cellulose II, it was concluded that it is possible to study the mechanism and kinetics of the diacetylation reaction of CDA nanofibers to cellulose II nanofibers and to quantify the ester bonds in the process of diacetylation of CDA nanofibers in an alkaline medium to cellulose II nanofibers [14].

Next, we carried out X-ray diffraction analysis of CDA nanofibers and hydrated cellulose nanofibers on a Miniflex600 device (Rigaku) at 40 kV and a current of 15 mA in the  $2\theta$  range of 3–40° [15].

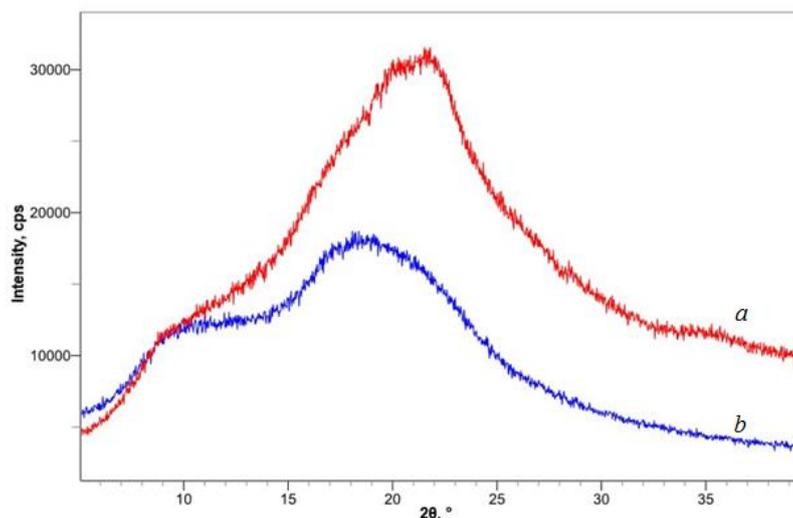

**Figure 3.** X-ray diffraction patterns of samples: a) CDA treated with KOH; b) CDA initial.

A wide amorphous halo is observed in the diffraction patterns of the original CDA nanofibers, fig. 3 (b), which confirms the information about the absence of long-range order, which is apparently related to the values of the degree of substitution of acetyl groups in CDA macromolecules, which prevent the formation of oriented structures, and confirms the transition of CDA macromolecules to an amorphous form. As can be seen from the CDA diffraction pattern, the amorphous halo has a bimodal shape, and maxima are observed in the regions  $2\theta = 10^\circ$  and  $19^\circ$ , which is apparently due to the formation of twisted amorphous structures in CDA nanofibers.

X-ray diffraction analysis of CDA nanofibers obtained by saponification in a 0.1 M solution of potassium hydroxide fig. 2 (a) shows that the occurrence of the diacetylation reaction leads to the formation of cellulose II nanofibers and the appearance of characteristic reflections of the crystalline structure of cellulose II, with a maximum at  $2\theta = 21^\circ$ .

The increase in the degree of crystallinity of cellulose nanofibers compared to CDA nanofibers is apparently explained by their transition to an oriented state during the diacetylation of acetyl groups in CDA nanofibers.

This, the possibility of obtaining cellulose II nanofibers by diacetylation of CDA nanofibers in an alkaline medium has been demonstrated. The resulting samples of cellulose nanofibers had an average diameter of 350–400 nm and a residual content of 4–6 acetyl groups per 100 anhydroglucose units. The degree of swelling of cellulose II nanofibers in water was 270–20%. The resulting nanofiber nonwoven cellulose fabrics have unique properties due to their large surface area per unit volume and can be widely used in the creation of air filters and in the medical practice of biodegradable wound coverings with hemostatic and bactericidal properties. By chemically modifying cellulose nanofibrous webs, it is possible to significantly expand the range of their practical applications.

#### 4. Conclusion

This study successfully demonstrated the formation of cellulose nanofibers from cellulose diacetate (CDA) via electrospinning using optimized acetone-water solvent mixtures, and the subsequent conversion of these nanofibers to cellulose II through saponification. The comparative analysis of CDA and cellulose II nanofibers using IR spectroscopy and X-ray diffraction revealed significant differences in their structural properties. The optimal conditions for producing CDA nanofibers were identified as acetone solutions containing 5–10% water, under specific electrospinning parameters.

These findings have important implications for the development of advanced cellulose-based nanomaterials, highlighting their potential practical applications in various fields. Further research is needed to explore the full range of applications for cellulose II nanofibrous nonwovens and to refine the production process for enhanced efficiency and scalability. This work was supported by the fundamental project FZ-4721055613, which focuses on the fundamental aspects of nanofiber formation based on high-molecular systems.

## REFERENCES

- [1] E. I. El-Aswar, H. Ramadan, H. Elkik, and A. G. Taha, "A comprehensive review on preparation, functionalization and recent applications of nanofiber membranes in wastewater treatment," *J. Environ. Manage.\**, vol. 301, p. 113908, 2022.
- [2] Y. Zhang, C. Zhang, and Y. Wang, "Recent progress in cellulose-based electrospun nanofibers as multifunctional materials," *Nanoscale Adv.\**, vol. 3, pp. 6040–6047, 2021.
- [3] M. A. Wsoo, S. Shahir, S. P. Mohd Bohari, N. H. M. Nayan, and S. I. A. Razak, "A review on the properties of electrospun cellulose acetate and its application in drug delivery systems: A new perspective," *Carbohydr. Res.\**, vol. 491, p. 107978, 2020.
- [4] X. Y. Wang, C. Drew, S. H. Lee, K. J. Senecal, J. Kumar, and L. A. Samuelson, "Nano Lett., 2, 173 (2002)."
- [5] H. Q. Liu and Y. L. Hsieh, "J. Polym. Sci., Part B: Polym. Phys., 40, 2119 (2002)."
- [6] W. K. Son, J. H. Youk, T. S. Lee, and W. H. Park, "J. Polym. Sci., Part B: Polym. Phys., 42, 5 (2004)."
- [7] E. W. Merrill, "Formation of Cellulose Nanofibers Based on Cellulose Diacetate," *Journal of Polymer Science Part B: Polymer Physics\**, vol. 42, no. 6, pp. 1068-1075, 2004.
- [8] X. Zhou, Y. Yu, S. Zhang, and J. Zhang, "Electrospun Cellulose Acetate Nanofibers as a Novel Adsorbent for Solid-Phase Extraction," *Materials Letters\**, vol. 62, no. 23, pp. 4056-4058, 2008.
- [9] L. A. Lucia, "Modification of Cellulose Fibers to Enhance Interactions with Polylactic Acid," *Journal of Natural Fibers\**, vol. 5, no. 4, pp. 22-35, 2008.
- [10] C. Luo and I. I. E. Arvanitoyannis, "The Effect of Polyols and Polycarboxylic Acids on the Properties of Thermoplastic Starch," *Polymer\**, vol. 49, no. 13-14, pp. 4087-4093, 2008.
- [11] R. A. Shanks, "Thermal and Mechanical Properties of Polymeric Blends Based on Cellulose Derivatives," *Journal of Applied Polymer Science\**, vol. 86, no. 12, pp. 3090-3098, 2002.
- [12] R. A. Shanks, "Thermal and Mechanical Properties of Polymeric Blends Based on Cellulose Derivatives," *Journal of Applied Polymer Science\**, vol. 86, no. 12, pp. 3090-3098, 2002.
- [13] T. Hattori, "Structural and Thermal Analysis of Cellulose Acetate Nanofibers Prepared by Electrospinning," *Polymer Journal\**, vol. 39, pp. 115-122, 2007.
- [14] Y. Kimura, "Synthesis and Properties of Cellulose-Based Nanocomposites," *Cellulose\**, vol. 14, pp. 167-176, 2007.
- [15] J. H. Lehmann, "Electrospinning of Cellulose Acetate/Polyethylene Oxide Blends," *Journal of Polymer Science Part B: Polymer Physics\**, vol. 43, no. 20, pp. 20475-20482, 2005.